

Reply to Comment

(Dated: February 6, 2008)

Our experiments [1, 2, 3] persuade us that the Meissner transition at T_c in hole-doped cuprates is driven by the loss of long-range phase coherence caused by singular phase fluctuations, a scenario at odds with the mean-field (MF), Gaussian Ginzburg Landau (GGL) approach advocated by Cabo, Mosquera and Vidal [4].

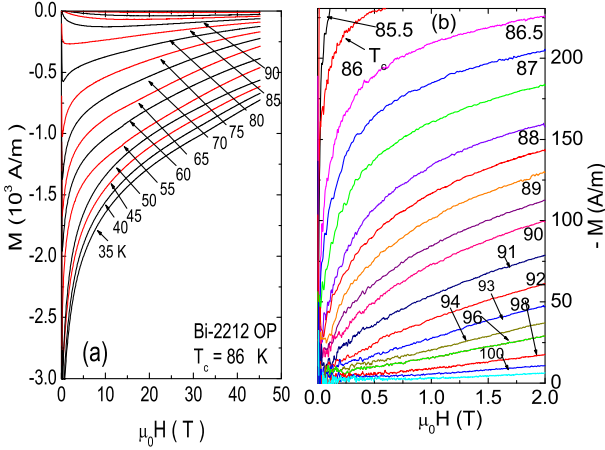


FIG. 1: (color online) Magnetization curves in OP Bi 2212. Panel a shows M measured up to 45 T at T from 35 K to above 90 K ($T_c = 86$ K). Below 70 K, $|M|$ decreases as $\log H$ over a very broad field interval [1], but above 70 K, M vs. H shows anomalous features such as the separatrix T_s (~ 85 K) at which M is independent of H below ~ 5 T. In large H , $|M|$ again decreases as $\log H$. $H_{c2}(T)$, defined as where $M \rightarrow 0$, remains high at values 100-150 T even when T_c is exceeded, in sharp contrast to GGL (MF) predictions (previous experiments on M stop at 5 T). Panel b displays the strong curvature of M above T_c in weak H (< 2 T) [2]. The curves display persistent negative curvature consistent with $M \sim -H^{1/\delta}$ with a T -dependent $\delta(T)$ up to ~ 105 K.

A characteristic MF feature is the linear decrease to zero of the upper critical field $H_{c2}(T) \sim (1 - t)$ near T_c ($t = T/T_c$, with T the temperature). In sharp contrast, magnetization (M) and Nernst data in intense fields H show that, in hole-doped cuprates, $H_{c2}(T)$ remains very large up to T_c [1, 2, 3]. Figure 1a shows curves of M

in optimal (OP) $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ (Bi 2212) measured in fields H to 45 T. The estimated H_{c2} values remain significantly higher than 45 T as T is raised above 86 K. The curves directly contradict previous, inferred $H_{c2} \sim (1 - t)$ behavior, mostly from data taken below 5 T (see Fig. 3 of Ref. [3] for curves in OP $\text{YBa}_2\text{Cu}_3\text{O}_7$).

A second incompatibility with the GGL approach is the striking nonlinearity of the M - H curves in Bi 2212 (Fig. 1b) [2]. Between 105 K and T_c , the magnetization displays the fractional power-law behavior $M \sim -H^{1/\delta}$ in weak fields [2]. The exponent $\delta(T)$ grows from 1 to ~ 15 as T falls from 105 K to T_c . This unusual field dependence is in conflict with the Gaussian treatment of fluctuations. Other incompatibilities with GGL theory include the anomalous increase in $|M|$ above H_{c1} for $T < T_c$ (see Ref. [2] for full discussion).

In light of the fundamental incompatibilities, fitting the T dependence of $M(T, H)$ at a *single* value of H is not an enlightening exercise. As shown in Ref. [2], $|M(T, H)|$ with $H = 10$ Oe actually diverges exponentially as T decreases towards T_c from above, instead of as a power-law in $(t - 1)$. Approaches based on phase-disordering schemes, e.g. the Kosterlitz-Thouless transition [6] or the anisotropic 3D XY model [8] seem more productive.

Further, the GGL fits lead to parameters that are highly unreliable. In optimal Bi 2212, the experiment gives $H_{c2}(0) = 150$ -200 T, whereas the fit in Ref. [4] predicts 330 T. In underdoped LSCO ($x = 0.1$), we find $H_{c2}(0) \sim 80$ T, whereas a similar analysis [5] predicts 26-28 T. Such a low H_{c2} is ruled out by experiment [3, 7].

Other evidence exist for the survival of the pair condensate amplitude high above T_c in the pseudogap state. These include the Nernst effect [3], kinetic inductance [9] and measurements of the gap [10, 11]. These anomalies are completely outside the purview of Gaussian fluctuations that underlie the GGL approach, regardless of the cut-off scheme adopted.

Lu Li¹, Yayu Wang¹, M. J. Naughton² and N. P. Ong¹

¹ Princeton University

² Boston College

- [1] Yayu Wang *et al.*, Phys. Rev. Lett. **95**, 247002 (2005).
- [2] L. Li *et al.*, Europhys. Lett. **72**, 451 (2005).
- [3] Yayu Wang, Lu Li and N. P. Ong, Phys. Rev. B **73**, 024510 (2006).
- [4] L. Cabo, J. Mosquera and F. Vidal, submitted Comment.
- [5] C. Carballera *et al.*, Physica C **384**, 185 (2003).
- [6] Vadim Oganessian, David A. Huse and S. L. Sondhi, Phys. Rev. B **73**, 094503 (2006).

- [7] Lu Li, J. G. Checkelsky, Seiji Komiya, Yoichi Ando and N. P. Ong, Nature Physics, *in press*.
- [8] A.K. Nguyen and Sudbø, Phys. Rev. B **60**, 15307 (1999).
- [9] J. Corson *et al.*, Nature **398**, 221 (1999).
- [10] Ch. Renner, B. Revaz, J.-Y. Genoud, K. Kadowaki, and Ø. Fischer, Phys. Rev. Lett. **80**, 149 (1998).
- [11] K. K. Gomes, A. N. Pasupathy, A. Yazdani *et al.*, *unpublished*.